Thermal Radiative Properties and Temperature Measurement from Turbine Coatings¹

James R. Markham^{2,3} and Karen Kinsella²

- 2 Advanced Fuel Research, Inc., 87 Church Street, East Hartford, CT 06108, U.S.A.
- 3 To whom correspondence should be addressed.

Paper presented at the Thirteenth Symposium on Thermophysical Properties, June 22-27, 1997, Boulder, Colorado, U.S.A.

ABSTRACT

Recent studies have revealed the spectral radiative properties of ceramic thermal barrier coatings which are finding applications in high performance turbine engines. As a function of temperature, a region in the long wavelength infrared spectrum exhibits properties which will minimize the classical errors associated with temperature measurement by radiometric detection. Hollow sapphire waveguides transmit the portion of the long wavelength infrared which is optimum for radiometric temperature measurement from these materials, while the physical properties of the sapphire can withstand the combustion conditions within the engine. A prototype long wavelength infrared thermometer was constructed to obtain surface temperature measurements from coated turbine blades subjected to high temperature combustion conditions.

KEY WORDS: ceramics; long wavelength infrared; radiation thermometer; thermal barrier coatings; thermal radiative properties; turbine engines

1. INTRODUCTION

Advanced thermal coating materials are being developed for use in the combustor section of high performance turbine engines [1]. Such coatings can provide a thermal barrier between metal components and hot gases allowing higher operational gas temperatures for improved turbine performance without component degradation. To optimize coating use, accurate surface temperature measurements are required to understand their response to changes in the combustion environment.

Radiation thermometry combined with fiber optics provides powerful sensors for determining surface temperatures in otherwise inaccessible locations [2]. However, typical instruments operate either in the short wavelength infrared (SWIR) or the visible portion of the electromagnetic spectrum to take advantage of the transmissive properties of widely used solid silica and sapphire fibers. Our laboratory [3] and others [4] have shown that ceramics which show promise as thermal barrier coatings (TBCs) in turbine engine applications have low, variable emissivities at short wavelengths, which lead to serious measurement inaccuracies. Combustion reflection has been shown to contribute up to 70% of the measured short wavelength signal [5] when used on TBCs where emissivity is low. Temperature measurements would be more accurate in the long wavelength infrared (LWIR) where ceramic TBC emissivities are typically high and stable (i.e., near-blackbody)[3,4].

Hollow sapphire waveguides have been employed for LWIR laser power delivery [6], and in LWIR remote spectroscopy [7]. Radiation is propagated in the air core of a hollow waveguide by total internal reflection; and due to optical properties, is limited in the case of sapphire to the delivery of LWIR. The spectral band is well suited to the region of near-blackbody radiative

characteristics of TBCs, while the high melting point (2053°C) and durability of sapphire allows waveguides to be placed near and in combustion environments.

This paper presents a prototype LWIR radiation thermometer for temperature measurement of TBCs used in high performance turbine engines. The sensor probe consists of a hollow sapphire waveguide to deliver the LWIR signal of the TBC to a detector. Temperature measurements from TBCs on substrates subjected to high temperature combustion conditions were obtained.

2. MEASUREMENTS

2.1. Prototype LWIR Radiation Thermometer

Figure 1 presents a schematic diagram of the hollow sapphire waveguide radiation thermometer. The durable hollow sapphire waveguide (25 cm long x 1450 μm O.D. x 1070 μm I.D.) was coupled to a hollow glass extension waveguide (2 m long). During measurements, the target LWIR radiance would enter the hollow sapphire waveguide, propagate through its length and through the length of the hollow glass waveguide from where it would be launched through the remaining components of the optical system. The optical components include: 1) a mechanical chopper to modulate the LWIR beam; 2) an aperture to limit the optical throughput of the system to the target signal; 3) a pair of plano-convex lenses to bring the LWIR beam to a focus on the detector; 4) a LWIR narrow bandpass filter to further limit the spectral region passed by the hollow waveguides; and 5) a LWIR detector that is sensitive to modulated radiance. The LWIR narrow bandpass filter exhibits a transmittance of 80% at the bandpass between 10-11.4 μm (1000-877 cm⁻¹). The filter is the most spectrally limiting component of the optical system and serves to: 1) allow LWIR radiance to pass that corresponds to the spectral region of near-blackbody emissivity of the TBCs studied; 2) eliminate spurious SWIR energy that can propagate

within the sapphire and glass walls of the hollow waveguides; and 3) eliminate significant LWIR interference from the large emission bands of hot, high pressure H₂O vapor and CO₂ gas generated in turbine combustors. Gas spectra were generated from the HITRAN spectroscopic database [8] at temperatures and pressures in the range expected in advanced turbines [5] to confirm the third service of the filter.

The sensor was calibrated by placing a temperature controlled near-blackbody surface in view of the hollow sapphire waveguide. The calibration curve (response function) generated from 100° C to 880° C agreed in shape with the curve generated from theoretical Planck function radiant intensity at the center wavelength of the bandpass filter for the same temperature range. The agreement in shape for the low temperature region indicated that the detector was linear with intensity. Due to the lack of a high temperature blackbody source, the theoretical Planck curve was used to extend the sensor calibration to 1600° C. Analysis of calibration data at 820° C indicated instrument stability to be within $\pm 2^{\circ}$ C($\pm 0.25\%$). Slight temperature fluctuations in the calibration target may have been a contributing factor.

2.2. Specimens

Two specimens with proprietary yittria-stabilized zirconia TBCs were provided by United Technologies Pratt & Whitney. The spectral emissivities were measured with our Fourier transform infrared (FT-IR) benchtop emissometer [9], and were high (0.97) as a function of wavelength, and stable as a function of temperature in the response region of the LWIR thermometer.

2.3. Procedure

The first measurements of TBC surface temperature by the LWIR thermometer were verified by measurements with an FT-IR emission spectrometer system [10]. Both instruments were arranged to simultaneously measure the temperature from the same 3mm diameter spot on the TBC test blade surface. To heat the test blade, a propane torch flame was applied to the back surface. As shown in Fig. 2, agreement was observed between the two instruments for both shape and amplitude of the traces. The LWIR thermometer was measuring at a rate of 5 data points per second, while the FT-IR spectrometer was significantly slower at 1 data point per six seconds. The FT-IR signal averaged several "scans" during the six seconds, so short term temperature changes are not as well resolved by the FT-IR method.

Similar temperature trace comparisons were made between the LWIR thermometer and fine wire thermocouples bonded adjacent to the 3 mm diameter spot. Thermocouples provided temperature traces similar in shape to the radiation thermometer, but generally 20-100°C lower due to expected deficiencies related to surface attachment and contact.

The prototype LWIR thermometer was also demonstrated for measurements at an atmospheric pressure combustion rig located at Pratt & Whitney in East Hartford, CT. The "Becon Burner" is designed to simulate the combustion processes that occur in large scale engines. The rig is equipped with a 2 inch diameter exhaust nozzle, and gas temperatures in the exhaust plume can reach 1500°C (2732°F). Figure 3 presents a photograph of the high temperature, high velocity exhaust of the Becon Burner with a test sample and the LWIR sensor mounted in position. Two configurations of the LWIR thermometer were utilized: 1) with the bare hollow sapphire waveguide exposed to the high temperature exhaust plume; and 2) with a water-cooled stainless steel jacket around the sapphire waveguide in the exhaust plume. For both

cases, successful temperature measurements were obtained with the receiving end of the sensor brought to 1 cm from the target surface.

Figure 4 presents two temperature traces obtained from a target spot 1.75 cm behind the leading edge of the test blade. In Fig. 4a, when a nominally constant burner condition was used, the blade surface temperature was maintained near 1220°C (2228°F). The temperature fluctuations (± 10°C or ±18°F) were expected due to the "flame flicker" of the exhaust gas stream. No alternative temperature sensing methods were available to corroborate the temperature measurements obtained for the test blade. However, the leading edge of the blade lost its TBC and the nickel alloy melted during the test. The melting point of this alloy is 1338°C (2440°F), so the readings obtained behind the leading edge were not unreasonable.

In Fig. 4b, the burner was quickly raised off the test blade (in less than 1/2 second) early in the trace, and the sensor recorded the blade cooling. Then the burner was re-positioned on the test blade (in less than 1/2 second), and temperature rise was recorded. Important to note from this experiment is that there was no significant evidence of extraneous radiance contributing to the temperature measurement. If radiance originating from, for example, the glowing burner nozzle or from inside the burner were reflecting into the field of view of the sensor, a more abrupt change in signal would occur when drastically shifting the burner position [11].

3. RESULTS

The LWIR radiation thermometer is well-suited to application on advanced high performance turbine engines since: 1) the operational wavelengths are optimized for the radiative properties of TBCs; and 2) the sapphire probe is optimized to survive the high temperature/pressure environment. HITRAN generated gas spectra as well as measurements of the Becon Burner exhaust in the absence of a test blade indicated minimal interference from

combustion products. Temperature measurements in our laboratory were confirmed by the FT-IR optical method and thermocouples. The radiation thermometer survived the combustion conditions of Pratt & Whitney's Becon Burner facility and recorded target temperatures.

Development of a fast response system to target first stage rotor blades is the next step in development.

ACKNOWLEDGEMENTS

This work was supported under U.S. DoE SBIR Phase I grant no. DE-FG02-96ER82112. Richard A. Johnson is the DoE project manager. Acknowledgments are given to Richard Strange, Fred Weisse, and Fred Fries of Pratt & Whitney for testing support; and to Jim Harrington of Rutgers University for supplying the hollow waveguides and suggestions. Gratitude is expressed to Bill Atkinson of Pratt & Whitney for arranging testing, supplying TBC samples, and continued dialogue pertaining to this work.


REFERENCES

- H.A. Webb and W.P. Parks, "Program to Develop Advanced Gas Turbine Systems," Air and Waste Management Association Annual Meeting, Cincinnati, Ohio, Conf. 940632-21 (June 19-24, 1994).
- 2 R. Vanzetti and A.C. Traub, in Theory & Practice of Radiation Thermometry, D.P. DeWitt and G.P. Nutter, eds. (Wiley, New York, 1988), Chapter 11.
- A.S. Bonanno, M.A. Serio, and J.R. Markham, "High Temperature Radiative Property Measurements of Advanced Turbine Materials," Proceedings of the NASA Remote Temperature Sensing Workshop, NASA Lewis Research Center, NASA Conference Publication 10167, (Oct. 27-28, 1994).
- W.H. Atkinson, and M.E. Cyr, "Evaluation of Sensors for Temperature Measurement of Ceramic Materials," Proc. of the 3rd Annual HITEMP Review, NASA Conference Publ., 10051, (1990).
- 5 E. Suarez, "Temperature Measurements of Thermal Barrier Coated Turbine Blades," Proceedings of the NASA Remote Temperature Sensing Workshop, NASA Lewis Research Center, NASA Conference Publication 10167, (Oct. 27-28, 1994).
- 6 J.A. Harrington, and C. Gregory, Opt. Lett., **15**, 541 (1990).
- 7 S.J. Saggese, J.A. Harrington, and G.H. Sigel, Jr., Optic Letters, **16**, 27 (1991).
- 8 L.S. Rothman, R. Gamache, R. Tipping, C. Rinsland, M. Smith, D. Benner, V. Devi Malathy, J.M. Flaud, C. Camry-Reyret, A. Perrin, A. Goldman, S. Massie, L. Brown, and R.J. Toth, Quant. Spectrosc. Radiat. Transfer, 48, 469 (1992).

- 9 J.R. Markham, K. Kinsella, R.M. Carangelo, C.R. Brouillette, M.D. Carangelo, P.E. Best, and P.R. Solomon, Rev. of Sci. Instr., **64**, (9), 2515, (1993).
- 10 P.W. Morrison, Jr., P.R. Solomon, M.A.Serio, R.M. Carangelo, and J.R. Markham, Sensors,8, (12) pp 32-38, and (13) pp 26-30, (1991).
- J.R. Markham, W.W. Smith, J.R. Haigis, M.D. Carangelo, J.E. Cosgrove, K. Kinsella, P.R. Solomon, P.E. Best, A. Lewandowski, C.E. Bingham, and J.R. Pitts, ASME Journal of Solar Energy Engineering, 118, 20 (1996).

FIGURE CAPTIONS

- **Figure 1.** Schematic of the prototype LWIR radiation thermometer.
- **Figure 2.** LWIR radiation thermometer measurements (solid line) vs. FT-IR spectrometer measurements (dashed line). The target was a test turbine blade with TBC.
- **Figure 3.** Photograph of the Becon Burner. A sample is supported in the exhaust plume, and the LWIR sensor is inserted from the far side to 1 cm from the target. The extension waveguide carries the target signal to the remote detector.
- **Figure 4.** LWIR thermometer temperature measurements from turbine blade with TBC in the Becon Burner flame. a) Constant burner setting; b) Trace obtained when burner flame was purposely raised above blade, then repositioned on blade. Note difference in temperature scales.

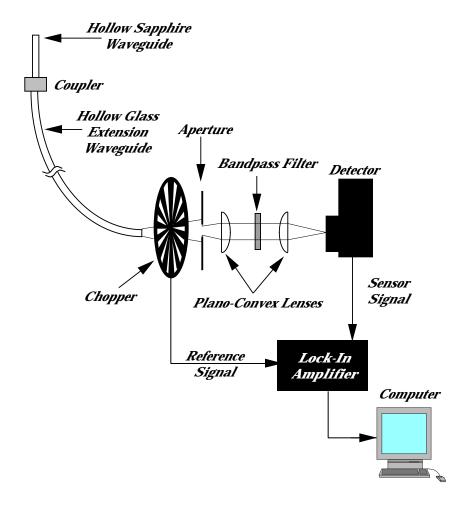


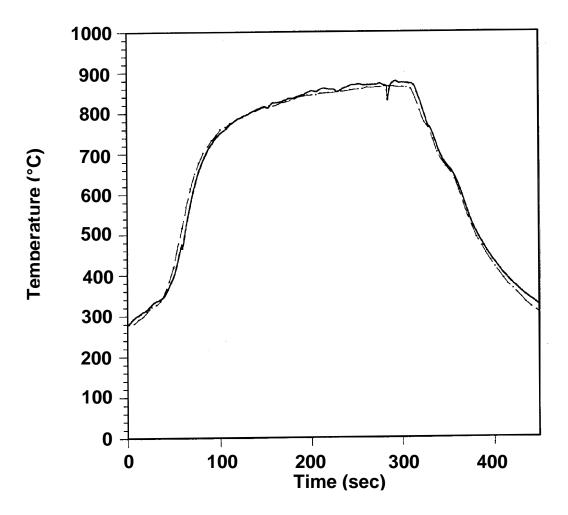


Figure 2. Markham et al.



Extension Waveguide

Sample Held up into Flame

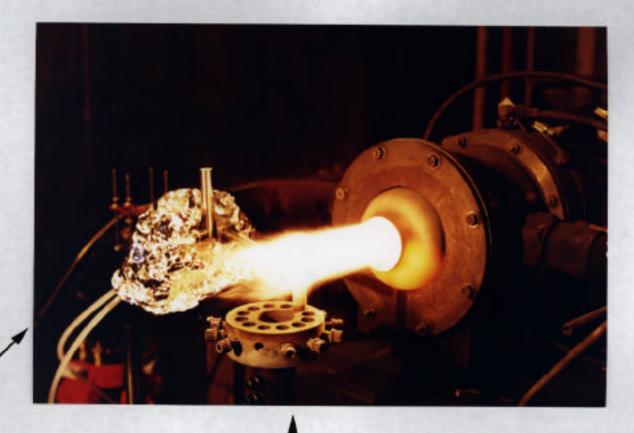